arXiv:cond-mat/0106549v1 [cond-mat.stat-mech] 26 Jun 2001

Physical Kinetics of Ferroelectric Hysteresis

S. Sivasubramanian and A. Widom
Physics Department, Northeastern University, Boston MA 02115

The physical kinetics of single domain ferroelectric materials are studied using Landau-Khalatnikov equation. The hysteretic curves are obtained numerically. The effective coercive electric field theoretically varies with the driving amplitude and frequency. The effects of thermal noise are explored using the Fokker-Planck kinetic equation. The ferroelectric switching times are discussed and Quantum effects are briefly explored.

PACS: 77.80.Dj, 77.80.Fm, 77.22.Gm

I. INTRODUCTION

Ferroelectric materials are endowed with a thermodynamic spontaneous electric dipole moment per unit volume $\mathbf{P}_s$ at a minimum of the free energy per unit volume $F(\mathbf{P},T)$. Both experimentally [1–18] and theoretically [19–28], the polarization can be changed in direction via a dynamic *switching* process accompanied by hysteresis [9,28–47]. Some of the partially understood experimental properties of ferroelectric domains [27,48–58] include the following: (i) No unique coercive field is evident during the hysteretic process of switching. [28–39] (ii) When an alternating electric field is applied, a hysteretic loop is observed only within a limited frequency band and a limited range of the amplitude-frequency product. [9,43–46] (iii) Formation of multiple hysteresis loops [47] are commonly observed.

From the thermodynamic viewpoint, one often assumes a phenomenological form for the free energy per unit volume $F(\mathbf{P},T)$ and employs the thermodynamic law

$$dF = -SdT + \mathbf{E}\cdot d\mathbf{P}. \tag{1}$$

The thermodynamic electric field is given by

$$\mathbf{E} = \left(\frac{\partial F}{\partial \mathbf{P}}\right)_T \quad \text{(equilibrium)}. \tag{2}$$

The phenomenological free energies adequately describe the equilibrium experimental properties of ferroelectric materials.

The dynamical hysteretic properties of the ferroelectric domains are less well studied from a theoretical viewpoint [31,40–42]. In principle, a changing polarization is equivalent to a current density $\mathbf{J} = (d\mathbf{P}/dt)$. One expects a current density to give rise to a non-equilibrium electric field $\mathbf{E}_{dynamical} = \rho\mathbf{J} = \rho(d\mathbf{P}/dt)$ where ρ is an "internal resistivity". The above argument leads to the Landau-Khalatnikov dynamical equation of motion [59–62],

$$\mathbf{E} = \left(\frac{\partial F}{\partial \mathbf{P}}\right)_T + \rho\left(\frac{d\mathbf{P}}{dt}\right) \quad (\text{non}-\text{equilibrium}). \tag{3}$$

The Landau-Khalatnikov Eq.(3) has been employed most often in the linearized form close to thermal equilibrium

$$\delta\mathbf{E} = \left(\frac{1}{\chi} + \rho\frac{d}{dt}\right)\delta\mathbf{P}, \tag{4}$$

where χ is the isothermal electric susceptibility. From the linearized Landau-Khalatnikov Eq.(4), one may deduce the relaxation time

$$\tau = \rho\chi. \tag{5}$$

While the relaxation time τ can be employed to estimate the switching time, it is evident that hysteretic loops are inherently non-linear. Our purpose is to solve the non-linear Landau-Khalatnikov Eq.(3) with a view towards a deeper theoretical understanding of ferroelectric hysteresis. The solutions to be discussed in the work which follows have been obtained numerically. The qualitative features deduced from the non-linear Landau-Khalatnikov Eq.(3) are in satisfactory agreement with experiment.

In Sec. II, the Landau-Khalatnikov equation is considered for the case in which the driving electric field has the form $\mathbf{E}(t) = \mathbf{E}_0\cos(\omega t)$. The numerically obtained hysteretic curves will be exhibited in Sec. III. In Sec. IV the effects of thermal noise are explored using the Fokker-Planck physical kinetic equation [63] for the probability distribution. The ferroelectric switching time is computed as a function of the applied electric field. In Sec. V we present the Lagrangian form of the equations of motion and extend the theory to include second derivative terms in the differential equation of motion. The quantum mechanical consequences of the Lagrangian formulation of the physical kinetics are discussed in Sec.VI. Future prospects for theoretical extensions are discussed in the concluding Sec. VII.

II. LANDAU-KHALATNIKOV EQUATION

To measure Hysteretic cycles one applies an electric field to the ferroelectric sample $\mathbf{E}(t) = \mathbf{E}_0\cos(\omega t)$. The Landau-Khalatnikov equation

$$\rho\left(\frac{d\mathbf{P}}{dt}\right) + \left(\frac{\partial F(\mathbf{P},T)}{\partial \mathbf{P}}\right) = \mathbf{E}_0\cos(\omega t), \tag{6}$$

then determines how the polarization $\mathbf{P}(t)$ responds in time. For a stable hysteretic curve, one looks for a periodic solution

$$\mathbf{P}\big(t+(2\pi/\omega)\big)=\mathbf{P}(t)\quad\text{(cyclic process)}. \tag{7}$$

If the polarization $\mathbf{P}=(0,0,P)$ and the applied electric field $\mathbf{E}=(0,0,E)$ are along an "easy axis", then Eq.(6) reads

$$\rho\left(\frac{dP}{dt}\right)+\left(\frac{\partial F(P,T)}{\partial P}\right)=E_0\cos(\omega t). \tag{8}$$

We choose for a model free energy, the Landau phenomenological form

$$F(P,T)=\left(\frac{1}{8\chi_0(T)P_s(T)^2}\right)\left(P^2-P_s(T)^2\right)^2, \tag{9}$$

where $P_s(T)$and $\chi_0(T)$ are, respectively, the polarization and electric susceptibility with a zero static electric field.

For the purpose of numerical integration of Eqs.(8) and (9), one may introduce the dimensionless quantities

$$\theta=\omega t,\quad x=(P/P_s),\quad\text{and}\quad y=(\chi_0 E/P_s). \tag{10}$$

Also

$$\eta=\left(\frac{1}{2\chi_0\rho\omega}\right)\quad\text{and}\quad z_0=\left(\frac{E_0}{\rho\omega P_s}\right). \tag{11}$$

Eqs.(8)-(11) now read

$$\left(\frac{dx}{d\theta}\right)+\eta x(x^2-1)=z_0\cos\theta. \tag{12}$$

To calculate a hysteretic loop one must numerically solve Eq.(12) subject to an initial condition $x(\theta=0)$. After integrating Eq.(12) over one period of 2π, one finds that

$$x(\theta=2\pi)=\mathcal{F}\big(x(\theta=0);\eta,z_0\big). \tag{13}$$

The initial condition $x(\theta=0)=x$ for a hysteretic loop $x(\theta+2\pi)=x(\theta)$ must be a fixed point of the function $\mathcal{F}$; i.e.

$$x=\mathcal{F}(x;\eta,z_0). \tag{14}$$

Such fixed points exist only for a limited region of values of the parameters (η,z_0). Thus, only for finite ranges of frequency ω and driving electric field E_0 in Eq.(8) will give rise to clean periodic hysteresis loops. For some regimes of frequency and driving electric field, the motion in the phase plane (E,P) will be chaotic. The limited range of parameters (η,z_0) for observing hysteretic periodic motions in the phase plane is in agreement with well known features observed in ferroelectric experiments.

III. NUMERICAL RESULTS

Employing Eqs.(1) and (9), we find that the thermodynamic electric field implied by the model under consideration,

$$E=\left(\frac{\partial F}{\partial P}\right)_T\quad\text{(equilibrium)}, \tag{15}$$

obeys

$$E=\left(\frac{P}{2\chi_0 P_s^2}\right)(P^2-P_s^2)\quad\text{(thermal)}. \tag{16}$$

The purely thermodynamic Eq.(16) gives rise to hysteretic behavior at a switching polarization of

$$P_{switch}=\left(\frac{P_s}{\sqrt{3}}\right), \tag{17}$$

which occurs at a coercive electric field of

$$E_c=\left(\frac{P_s}{3\chi_0\sqrt{3}}\right)=\left(\frac{P_{switch}}{3\chi_0}\right). \tag{18}$$

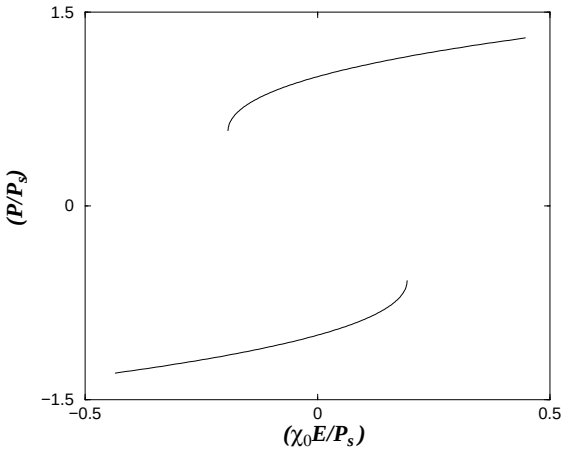

FIG. 1. Shown is a metastable thermal switching hysteresis curve calculated from Eq.(16). If the applied field starts negatively at $E<-E_c$ and the applied field is subsequently quasi-statically increased, then the polarization follows the lower curve and jumps to the upper curve when the coercive field E_c is exceeded.

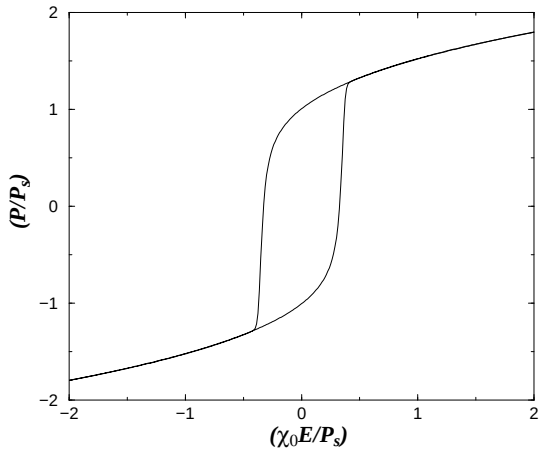

FIG. 2. The above plot is a numerically simulated hysteric loop calculated from the Landau-Khalatnikov model. The parameters chosen were $\eta=50.0$ and $z_0=200.0$.

When a cyclic process is numerically simulated for the case of finite frequency as in FIG.2, the resulting hysteretic loop looks qualitatively similar to the thermodynamic FIG.1.

However, there are quantitative features which depend on the magnitude of the frequency and the amplitude of the applied oscillating electric field. For example the dynamical "coercive field" deduced from the numerical simulations at finite frequency is quite different from the static thermodynamic "coercive field". Furthermore, the "shape" of the hysteretic loop depends strongly on the product of the frequency and the internal resistivity via $2\eta = (\chi_0 \rho \omega)^{-1}$. This point is illustrated in FIG.3.

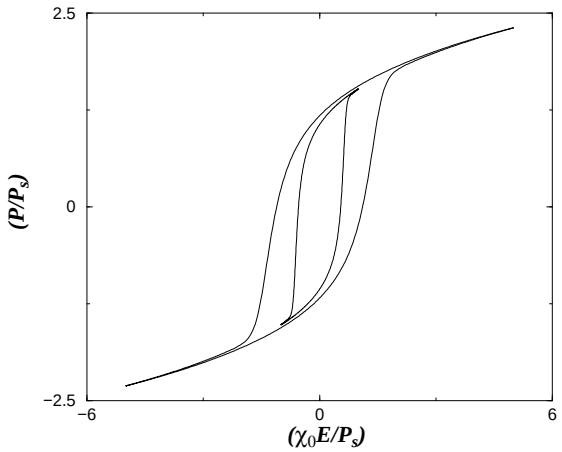

FIG. 3. Two *different* numerically simulated hysteretic loops are shown. The smaller (inner) loop corresponds to the values $\eta = 5.0$ and $z_0 = 10.0$. The larger (outer) loop corresponds to the values $\eta = 5.0$ and $z_0 = 50.0$. The two loops correspond to the same frequency. However, the larger loop is induced by the larger amplitude of the applied electric field.

It is evident, that the dynamically induced coercive field (for fixed frequency) depends on the amplitude of the applied electric field. Thus, the large (outer) hysteretic loop in FIG.3 has a much larger dynamic coercive field than does the small (inner) hysteretic loop. It is not in general possible to deduce the thermodynamic coercive field of Eq.(18) by the observation of a single dynamical hysteretic loop. From an experimental point of view, this ambiguity in determining the thermodynamic coercive field is a long standing problem.

IV. THERMAL NOISE

The existence of an internal resistivity ρ in the Landau-Khalatnikov Eq.(3) requires a thermally fluctuating electric field $\Delta\mathbf{E}(t)$; i.e. Eq.(3) with the inclusion of electric field noise reads

$$\rho\left(\frac{d\mathbf{P}}{dt}\right) = \mathbf{E} - \left(\frac{\partial F}{\partial \mathbf{P}}\right)_T + \Delta\mathbf{E}. \tag{19}$$

We have included "white noise" field fluctuations obeying

$$\overline{\Delta\mathbf{E}(t)\Delta\mathbf{E}(t')} = \left(\frac{k_B T}{\Omega}\right)\rho\mathbf{1}\delta(t-t'). \tag{20}$$

If $W(\mathbf{P},t)d^3\mathbf{P}$ denotes the probability for $\mathbf{P} \in d^3\mathbf{P}$, then the electric field noise in Eqs.(19) and (20) give rise to the Fokker-Planck equation

$$\rho\frac{\partial W}{\partial t} = \frac{\partial}{\partial \mathbf{P}}\cdot\left\{\left(\frac{\partial G}{\partial \mathbf{P}}\right)_{\mathbf{E},T} W + \left(\frac{k_B T}{\Omega}\right)\frac{\partial W}{\partial \mathbf{P}}\right\}, \tag{21}$$

where

$$G(\mathbf{P},\mathbf{E},T) = F(\mathbf{P},T) - \mathbf{E}\cdot\mathbf{P}. \tag{22}$$

In thermal equilibrium, the probability is determined by

$$W_{eq}(\mathbf{P}) = \exp\left(\frac{\Omega\big(A(\mathbf{E},T) - G(\mathbf{P},\mathbf{E},T)\big)}{k_B T}\right), \tag{23}$$

where $A(\mathbf{E},T)$ is determined by the total probability normalization

$$\int W_{eq}(\mathbf{P})d^3\mathbf{P} = 1. \tag{24}$$

If the polarization $\mathbf{P} = (0,0,P)$ and the applied electric field $\mathbf{E} = (0,0,E)$ are along an "easy axis", then it is sufficient to use a one-dimensional probability $W(P,t)dP$ for $P \in dP$ which obeys a one-dimensional Fokker-Planck equation

$$\rho\frac{\partial W}{\partial t} = \frac{\partial}{\partial P}\left\{\left(\frac{\partial G}{\partial P}\right)_{E,T} W\right\} + \left(\frac{k_B T}{\Omega}\right)\frac{\partial^2 W}{\partial P^2}\ . \tag{25}$$

The "jump time" associated with Eq.(25) may be computed in a well known manner. Suppose that the polarization at time zero is given by $P(t=0) = P_i$. With a final polarization $P_f > P_i$, let $\tau[P_f, P_i]$ be the mean "first passage time" for the polarization to move from a region $P < P_f$ to the complimentary region $P > P_f$. In detail, let t^* be the smallest positive time for which $P(t^*) = P_f$. The mean first passage time is then $\tau = \overline{t^*}$.

The closed form expression for the mean first passage time is well known to be

$$\tau[P_f,P_i] = \left(\frac{\Omega\rho}{k_B T}\right)\times$$

$$\int_{P_i}^{P_f}\int_{-\infty}^{P} e^{\Omega\left(G(P,E,T)-G(P',E,T)\right)/k_B T}dP'dP. \tag{26}$$

In principle, it is possible to solve the equation

$$t = \tau[P_f,P_i] \tag{27}$$

for the final polarization

$$P_f = P(t; P_i). \tag{28}$$

Eqs.(26), (27) and (28) imply

$$\rho\left(\frac{\partial P}{\partial t}\right) + \left(\frac{\partial F}{\partial P}\right)_T = E + \tilde{E}, \tag{29}$$

where

$$\left(\frac{\partial P}{\partial t}\right)^2 \tilde{E} = -\left(\frac{k_B T}{\Omega}\right)\left(\frac{\partial^2 P}{\partial t^2}\right). \tag{30}$$

In the limit of large single domains $\Omega \to \infty$, we have $\tilde{E} \to 0$ so that Eq.(29) becomes equivalent to the Landau-Khalatnikov Eq.(3). When $|\tilde{E}| << |E|$, then the Landau-Khalatnikov equation is sufficiently accurate for computing first passage times. However, very near critical temperatures and or critical electric (coercive) fields, a finite domain can switch due to thermal noise. The integral in Eq.(26) for the first passage time must then be evaluated.

V. LAGRANGIAN FORMULATION

In order to understand the extended Landau-Khalatnikov-Tani equation [64] for ferroelectric single domains, let us first review the extended Landau-Lifshitz-Gilbert equations [65,66] for ferromagnetic single domains. For the ferromagnetic case, there exists a free energy per unit volume $F(\mathbf{M}, T)$ which obeys the thermodynamic law

$$dF = -SdT + \mathbf{H} \cdot d\mathbf{M}. \tag{31}$$

The thermodynamic magnetic intensity is given by

$$\mathbf{H} = \left(\frac{\partial F}{\partial \mathbf{M}}\right)_T \quad \text{(equilibrium)}. \tag{32}$$

For non-equilibrium situations in an applied magnetic intensity $\mathbf{H}$, there is an effective field

$$\mathbf{H}_{eff} = \mathbf{H} - \left(\frac{\partial F}{\partial \mathbf{M}}\right) - \rho\left(\frac{\partial \mathbf{M}}{\partial t}\right), \tag{33}$$

The equation of motion for the magnetization then reads

$$\left(\frac{\partial \mathbf{M}}{\partial t}\right) = \gamma \mathbf{M} \times \mathbf{H}_{eff}, \tag{34}$$

where γ is the gyromagnetic ratio.

For the case of a Ferroelectric, Eqs.(1) and (2) replace Eqs.(31) and (32), and the effective magnetic intensity Eq.(33) is replaced by the effective electric field

$$\mathbf{E}_{eff} = \mathbf{E} - \left(\frac{\partial F}{\partial \mathbf{P}}\right)_T - \rho\left(\frac{\partial \mathbf{P}}{\partial t}\right). \tag{35}$$

While in the Landau-Khalatnikov theory, the effective field $\mathbf{E}_{eff}$ is set to zero, the Tani extension to the Landau-Khalatnikov theory includes an inertial term of the form

$$4\pi\left(\frac{\partial^2 \mathbf{P}}{\partial t^2}\right) = \omega_p^2 \mathbf{E}_{eff}. \tag{36}$$

Let us consider Eq.(36) in more detail. The dipole moment of N charged particles in a volume Ω is defined as

$$\Omega \mathbf{P} = \sum_{j=1}^{N} e_j \mathbf{r}_j, \tag{37}$$

where $\mathbf{r}_j$ is the position of the j^{th} particle with charge e_j. From the equation of motion for the j^{th} particle with mass m_j,

$$m_j \ddot{\mathbf{r}}_j = e_j \mathbf{E}_{eff} \tag{38}$$

and Eq.(37) one easily obtains Eq.(36) wherein ω_p can be identified with the plasma frequency

$$\omega_p^2 = \left(\frac{4\pi}{\Omega}\right)\sum_{j=1}^{N}\left(\frac{e_j^2}{m_j}\right). \tag{39}$$

Eqs.(35) and (36) yield the Landau-Khalatnikov-Tani theory for ferroelectric domains; i.e.

$$\left(\frac{4\pi}{\omega_p^2}\right)\left(\frac{\partial^2 \mathbf{P}}{\partial t^2}\right) + \rho\left(\frac{\partial \mathbf{P}}{\partial t}\right) + \left(\frac{\partial F}{\partial \mathbf{P}}\right)_T = \mathbf{E}. \tag{40}$$

Eq.(40) may be written in terms of the effective Lagrangian $L = \Omega\mathcal{L}$;

$$\mathcal{L} = \left(\frac{2\pi}{\omega_p^2}\right)\left(\frac{\partial \mathbf{P}}{\partial t}\right)^2 - F(\mathbf{P}, T) + \mathbf{E} \cdot \mathbf{P} \tag{41}$$

and the Rayleigh dissipation function $R = \Omega\mathcal{R}$;

$$2\mathcal{R} = \rho\left(\frac{\partial \mathbf{P}}{\partial t}\right)^2. \tag{42}$$

We have

$$\frac{\partial}{\partial t}\left(\frac{\partial \mathcal{L}}{\partial(\partial \mathbf{P}/\partial t)}\right) = \left(\frac{\partial \mathcal{L}}{\partial \mathbf{P}}\right) - \left(\frac{\partial \mathcal{R}}{\partial(\partial \mathbf{P}/\partial t)}\right). \tag{43}$$

The canonical "momentum" $\mathbf{\Pi}$ conjugate to the polarization $\mathbf{P}$ may be defined by

$$\mathbf{\Pi} = \Omega\left(\frac{\partial \mathcal{L}}{\partial(\partial \mathbf{P}/\partial t)}\right) = \left(\frac{4\pi\Omega}{\omega_p^2}\right)\left(\frac{\partial \mathbf{P}}{\partial t}\right). \tag{44}$$

Employing the Lagrangian viewpoint, one may quantize the single ferroelectric domain theory in the usual manner.

VI. QUANTUM KINETICS

In the fully quantum mechanical theory one expects the canonical commutation relation

$$[\mathbf{\Pi}, \mathbf{P}] = -i\hbar \mathbf{1} \tag{45}$$

which may also be proved employing a microscopic view. From Eq.(37) and (44) it follows (with $\dot{\mathbf{r}}_j = \mathbf{v}_j$) that

$$\mathbf{\Pi} = \left(\frac{4\pi}{\omega_p^2}\right) \sum_{j=1}^{N} e_j \mathbf{v}_j. \tag{46}$$

From the microscopic commutation relation

$$[\mathbf{v}_i, \mathbf{r}_j] = -\left(\frac{i\hbar\delta_{ij}}{m_j}\right) \mathbf{1}, \tag{47}$$

together with Eqs.(37), (39) and (46) follows the macroscopic quantum mechanical commutator in Eq.(45). One representation of the quantum mechanical operator $\mathbf{\Pi}$ is defined by

$$\mathbf{\Pi} = -i\hbar \left(\frac{\partial}{\partial \mathbf{P}}\right). \tag{48}$$

Forming the Hamiltonian from the Lagrangian in the standard canonical formalism,

$$\Omega \mathcal{H}_{eff} = \mathbf{\Pi} \cdot \mathbf{P} - \Omega \mathcal{L}, \tag{49}$$

yields the effective Hamiltonian for a ferroelectric domain

$$\Omega \mathcal{H}_{eff} = \left(\frac{\omega_p^2}{8\pi\Omega}\right) \mathbf{\Pi}^2 + \Omega \left\{F(\mathbf{P}, T) - \mathbf{E} \cdot \mathbf{P}\right\}. \tag{50}$$

where Eqs.(41), (44) and (49) have been invoked. Eqs.(48) and (50) describe a single domain ferroelectric grain in macroscopic quantum mechanical form.

From Eqs.(9), (48) and (50) one may compute the quasi-classical approximation for the quantum tunneling switching time. At zero electric field $\mathbf{E} = 0$, the quantum transition rate per unit time to switch polarizations (say $\mathbf{P}_s \rightarrow -\mathbf{P}_s$) is given by

$$\left(\frac{1}{\tau_0}\right)_{quantum} \approx \gamma_0 \exp(-B_0) \tag{51}$$

with a barrier factor given by

$$B_0 = \frac{8}{3}\sqrt{\frac{\pi}{\chi_0}} \left(\frac{\Omega P_s^2}{\hbar\omega_p}\right), \tag{52}$$

and an attempt frequency of

$$\gamma_0 = \left(\frac{2\omega_0}{\pi}\right) \sqrt{\frac{2\Omega U_0}{\hbar\omega_0}}. \tag{53}$$

In Eq.(53), the Barrier energy per unit volume is

$$U_0 = \left(\frac{P_s^2}{8\chi_0}\right) \tag{54}$$

and

$$\omega_0^2 = \left(\frac{\omega_p^2}{4\pi\chi_0}\right). \tag{55}$$

Thus

$$B_0 = \frac{32}{3} \left(\frac{\Omega U_0}{\hbar\omega_0}\right). \tag{56}$$

Quantum tunneling through the barrier will dominate classical thermal activation over the barrier if

$$\exp(-B_0) >> \exp(-\Omega U_0/k_B T). \tag{57}$$

Thus for temperatures small on the scale of

$$T^* = \left(\frac{\Omega U_0}{k_B B_0}\right) = \left(\frac{3\hbar\omega_0}{32 k_B}\right), \tag{58}$$

quantum tunneling will dominate classical thermal activation. For typical laboratory samples $T << T^*$ so that the life-time of domains for very small volume domains is dominated by quantum mechanics. Nevertheless, for large volume domains there is stability and the kinetics are well described by the Landau-Khalatnikov kinetic equation.

VII. CONCLUSION

We have shown that physical kinetics, via the Landau-Khalatnikov equation, adequately describes laboratory hysteretic behavior for large volume single domain ferroelectric materials. The important physical quantities include the amplitude and frequency dependence of the effective coercive electric field. The formalism describing thermal noise as well as quantum noise have been explored. Both forms of noise are unimportant for large volume ferroelectric domains. In the small domain volume limit, quantum noise effects dominate the classical thermal noise effects at laboratory temperatures substantially below the critical temperature.

The technical importance of ferroelectric switching times for small ferroelectric domain volumes is well documented [1–18]. The computation of switching times requires mesoscopic quantum mechanical models. Thus far, the theory of such quantum switches is in its infancy.

[1] W. J. Merz, *Phys. Rev.* **95**, 690 (1954).
[2] W. J. Merz, *J. Appl. Phys.* **27**, 938 (1956).

[3] M. Prutton, *Proc. Phys. Soc.* (London) **B70**, 1064 (1957).
[4] H. H. Weider, *Proc. Inst. Radio Engrs.* **45**, 1094 (1957).
[5] H. L. Stadler, *J. Appl. Phys.* **29**, 1485 (1958).
[6] H. H. Weider, *Phys. Rev.* **110**, 29 (1958).
[7] K. Zen'itit, K. Husumi and K. Kataoka, *J. Phys. Soc. Japan.* **13**, 661 (1958).
[8] K. Husumi and K. Kataoka, *J. Appl. Phys.* **B13**, 549 (1958).
[9] C. F. Pulvari and W. Küebler, *J. Appl. Phys.* **29**, 1742 (1958).
[10] M. Prutton, *J. Brit. Inst. Radio Engrs.* **19**, 93 (1959).
[11] G. J. Goldsmith and J. G. White, *J. Chem. Phys.* **31**, 1175 (1959).
[12] E. Fatuzzo and W. J. Merz, *Phys. Rev.* **116**, 61 (1959).
[13] E. Fatuzzo, *Helv. Phys. Acta.* **33**, 21 (1960).
[14] E. Fatuzzo, *Helv. Phys. Acta.* **33**, 429 (1960).
[15] E. Fatuzzo, *Proc. Phys. Soc.* (London) **76**, 797 (1960).
[16] E. Fatuzzo, G. Harbeke, W. J. Merz, R. Nitsche, H. Roetschi and W. Ruppel, *Phys. Rev.* **127**, 2036 (1962).
[17] H. H. Weider, *J. Appl. Phys.* **35**, 1224 (1964).
[18] B. Bingelie and E. Fatuzzo, *J. Appl. Phys.* **36**, 1431 (1965).
[19] E. Fatuzzo, *Phys. Rev.* **127**, 1999 (1962).
[20] Y. Ishibashi and Y. Takagi, *J. Phys. Soc. Jpn.* **31**, 506 (1971).
[21] N. Nakatani, *Jpn. J. Appl. Phys. Suppl.* **28-2**, 143 (1989).
[22] Y. Ishibashi, *Integr. Ferroelectrics* **2**, 41 (1991).
[23] S. Fahy and R. Merlin *Phys. Rev. Lett.* **73**, 1122 (1994).
[24] B. D. Qu, W. L. Zhong and R. H. Prince, *Phys. Rev. B* **55**, 11218 (1997).
[25] J. F. Scott, *Ferroelectr. Rev.* **1**, 1 (1998).
[26] O. Auciello, J. F. Scott and R. Ramesh *Phys. Today* **51**, 22 (1998).
[27] D. E. Steinhauer and S. M. Anlage, *J. Appl. Phys.* **89**, 2314 (2001).
[28] D. Ricinschi, C. Harnagae, C. Ppusoi, L. Mitoseriut, V. Tura and M. Okuyama, *J. Phys. Condens. Matter* **10**, 477 (1998).
[29] B. Xu, Y. Ye, L. E. Cross, J. J. Bernstein and R. Miller, *J. Appl. Phys.* **74**, 3549 (1999).
[30] C. J. Dias and D. K. Das-Gupta, *J. Appl. Phys.* **74**, 6317 (1993).
[31] T. Hauke, V. Muller, H. Beige and J. Fousek, *J. Appl. Phys.* **79**, 7658 (1996).
[32] J.-M. Liu, H. P. Li, C. K. Ong and L. C. Lim, *J. Appl. Phys.* **86**, 5198 (1999).
[33] Y. Xu, *Ferroelectric Materials and their Applications* (Elsevier Science, Amsterdam, 1991).
[34] L. Kim, J. Kim, D. Jung and Y. Roh,*J. Appl. Phys.* **76**, 1881 (2000).
[35] C. Bedoya, Ch. Muller, J.-L. Baudour, V. Madigou, M. Anne, M. Roubin, *Materials Science and Engineering* **B75**, 43 (2000).
[36] T. Yoshimura, N. Fujimura and T. Ito, *Appl. Phys. Lett.* **73**, 414 (1998).
[37] S. Ducharme, V. M. Fridkin, A. V. Bune, S. P. Palto, L. M. Blinov, N. N. Pethukova and S. G. Yudin, *Phys. Rev. Lett.* **84**, 175 (2000).
[38] M. E. Lines and A. M. Glass, *Principles and Applications of Ferroelectrics and Related Materials* (Clarendon, London, 1977), pp. 81-86.
[39] Z. Zhong, W. Ding, Y. Chen, X. Chen, Y. Zhu and N. Min, *Appl. Phys. Lett.* **75**, 1958 (1999).
[40] B. G. Potter Jr., V. Tikare, and B. A. Tuttle, *J. Appl. Phys.* **87**, 4415 (2000).
[41] D. Veihland and Y.-H. Chen, *J. Appl. Phys.* **88**, 6696 (2000).
[42] K.-H. Chew, L.-H. Ong, J. Osman and D. R. Tilley, *Appl. Phys. Lett.* **77**, 2755 (2000).
[43] R. Landauer, D. R. Young and E. M. Drougard, *J. Appl. Phys.* **27**, 752 (1956).
[44] V. Janovec, *Czech. J. Phys.* **8**, 3 (1958).
[45] Y. Ishibashi and H. Orihara, *Integr. Ferroelectr.* **9**, 57 (1995).
[46] J. F. Scott, B. Poulingy, K. Dimmler, M. Parris, D. Buttler and S. Eaton, *J. Appl. Phys.* **62**, 4510 (1987).
[47] Y. Naohiko and M. Takuya, *Appl. Phys. Lett.* **66**, 571 (1995).
[48] M. N. Kamalasanan, N. Deepak Kumar and Subhas Chandra, *J. Appl. Phys.* **74** , 5679 (1993).
[49] H. Ohigashi, N. Kagami and G. R. Li *J. Appl. Phys.* **71**, 506 (1992).
[50] V. Likodimos, X. K. Orlik, L. Pardi, M. Labardi and M. Allegrini, *J. Appl. Phys.* **87**, 443 (2000).
[51] F. Saurenbach and B. D. Terris, *Appl. Phys. Lett.* **56**, 1703 (1990).
[52] R. Lüthi, H. Haefke, K. -P. Meyer, E. Meyer, L. Howald and H. - J. Güntherodt, *J. Appl. Phys.* **74**, 7461 (1993).
[53] O. Kolosov, A. Gruverman, J. Hatano, K. Takahashi and H. Tokumoto, *Phys. Rev. Lett.* **74**, 4309 (1995).
[54] G. Zavala, J. H. Fendler and S. Trolier-McKinstry, *J. Appl. Phys.* **81**, 7480 (1997).
[55] C. Bedoya, Ch. Muller, J. -L. Baudour, V. Madigou, M. Anne, M. Roubin, *Materials Science and Engineering* **B75**, 43 (2000).
[56] S. Zhu and W. Cao, *Phys. Stat. Sol. A* **173**, 495 (1999).
[57] L. M. Eng, et al., *Ferroelectrics* **222**, 153 (1999).
[58] X. Zhu, J. Zhu, S. Zhou, Q. Li, Z. Liu and N. Ming *J. Appl. Phys.* **89**, 5079 (2001).
[59] L. D. Landau and I. M. Khalatnikov, *Dok. Akad. Nauk SSSR.* **46**, 469 (1954).
[60] S. Machlup and L. Onsager, *Phys. Rev.* **91**, 1505 (1953).
[61] S. Machlup and L. Onsager, *Phys. Rev.* **91**, 1512 (1953).
[62] Y. Makita, I. Seo and M. Sumita, *J. Phys. Soc. Japan.* **28**, Suppl. 268 (1970).
[63] H. Risken, *The Fokker-Planck Equation.* (Springer, Berlin. 1996).
[64] K. Tani, *J. Phys. Soc. Japan.* **26**, 93 (1969).
[65] L. Landau and L. Lifshitz, *Phys. Zeit. Sowjetunion.* **8**, 153 (1935).
[66] T. A. Gilbert, *Armor Research Foundation Rep. No. 11* Chicago, IL. (1955).